

2

# DTIC FILE COPY

Office of Naval Research

Contract N0014-85-K-0632

R & T Code 413c014

Technical Report No. 17



AD-A222 258

"DIRECT EVIDENCE FOR THE CREATION OF MICROPORES IN UV-IRRADIATED POLY(METHYL METHACRYLATE)"

by

J. A. Moore and Jin O Choi

To Be Published in

Proceedings of the Materials Research Society  
Fall, 1989, Boston, MA

Department of Chemistry  
Rensselaer Polytechnic Institute  
Troy, New York 12180-3590

|                    |                                     |
|--------------------|-------------------------------------|
| Accession For      |                                     |
| NTIS GRA&I         | <input checked="" type="checkbox"/> |
| DTIC TAB           | <input checked="" type="checkbox"/> |
| Unannounced        | <input type="checkbox"/>            |
| Justification      |                                     |
| By                 |                                     |
| Distribution/      |                                     |
| Availability Codes |                                     |
| Dist               | Avail and/or Special                |
| A-1                |                                     |

DTIC  
ELECTE  
JUN 05 1990  
S E D

May 31, 1990

Reproduction in whole or in part is permitted for any purpose of the United States Government.

This document has been approved for public release and sale; its distribution is unlimited.

90 06 04 184

# REPORT DOCUMENTATION PAGE

|  |       |   |   |  |                            |
|--|-------|---|---|--|----------------------------|
| 1a. REPORT SECURITY CLASSIFICATION<br>Unclassified   |       |   | 1b. RESTRICTIVE MARKINGS  |  |                            |
| 2a. SECURITY CLASSIFICATION AUTHORITY  |       |   | 3. DISTRIBUTION/AVAILABILITY OF REPORT<br>Approved for public release distribution unlimited. |  |                            |
| 2b. DECLASSIFICATION/DOWNGRADING SCHEDULE  |       |   | 5. MONITORING ORGANIZATION REPORT NUMBER(S)   |  |                            |
| 4. PERFORMING ORGANIZATION REPORT NUMBER(S)  |       |   | 7a. NAME OF MONITORING ORGANIZATION<br>ONR  |  |                            |
| 6a. NAME OF PERFORMING ORGANIZATION  |       | 6b. OFFICE SYMBOL<br>(if applicable)            |   | 7b. ADDRESS (City, State, and ZIP Code)<br>Department of Navy<br>Arlington, VA 22217 |                            |
| 6c. ADDRESS (City, State, and ZIP Code)  |       | 9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER |   |  |                            |
| 8a. NAME OF FUNDING/SPONSORING ORGANIZATION<br>ONR   |       | 8b. OFFICE SYMBOL<br>(if applicable)            |   | 10. SOURCE OF FUNDING NUMBERS  |                            |
| 8c. ADDRESS (City, State, and ZIP Code)<br>Department of Navy<br>Arlington, VA 22217   |       | PROGRAM ELEMENT NO.<br>N0014-85-K-0632          |   | TASK NO.<br>625-826  | WORK UNIT<br>ACCESSION NO. |
| 11. TITLE (Include Security Classification)<br>TECH. REP. # DIRECT EVIDENCE FOR THE CREATION OF MICROPORES IN UV-IRRADIATED POLY-(METHYL METHACRYLATE). (Unclassified)   |       |   |   |  |                            |
| 12. PERSONAL AUTHOR(S)<br>J.A. MOORE & JIN O CHOI  |       |   |   |  |                            |
| 13a. TYPE OF REPORT<br>Publication   |       | 13b. TIME COVERED<br>FROM TO                    |   | 14. DATE OF REPORT (Year, Month, Day)<br>May 31, 1990                                |                            |
| 15. PAGE COUNT   |       |   |   |  |                            |
| 16. SUPPLEMENTARY NOTATION<br>PROC. MAT. RES. SOC.   |       |   |   |  |                            |
| 17. COSATI CODES   |       |   | 18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number).            |  |                            |
| FIELD  | GROUP | SUB-GROUP                                       | Polymers, PMMA, Benzene Compounds, Porous Materials, Irradiation, Isomerization (56)          |  |                            |
|  |       |   |   |  |                            |
| 19. ABSTRACT (Continue on reverse if necessary and identify by block number)<br>Films of (PMMA) including azobenzene were prepared by casting polymer solutions containing the probe or by exposing pre-irradiated films to the vapor of azobenzene. Under similar conditions, films which had been irradiated imbibed more azobenzene than annealed, unirradiated films or irradiated films which had been annealed above (T <sub>g</sub> ). These materials were irradiated at 335 (nm) and the amount of trans azobenzene which had been formed was monitored spectrophotometrically. The largest amount of photoisomerization was observed for the pre-irradiated samples which had been penetrated by azobenzene from the vapor, indicating that the created free volume allowed the isomerization to proceed more easily.<br><br>Poly-Methyl Methacrylate      glass transition temperature nanometers |       |   |   |  |                            |
| 20. DISTRIBUTION/AVAILABILITY OF ABSTRACT<br><input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS  |       |   | 21. ABSTRACT SECURITY CLASSIFICATION<br>Unclassified  |  |                            |
| 22a. NAME OF RESPONSIBLE INDIVIDUAL<br>Kenneth J. Wynne  |       |   | 22b. TELEPHONE (Include Area Code)<br>(202) 696-4410  |  | 22c. OFFICE SYMBOL         |

# DIRECT EVIDENCE FOR THE CREATION OF MICROPORES IN UV-IRRADIATED POLY(METHYL METHACRYLATE)

J. A. MOORE\* and JIN-O CHOI\*

\*Rensselaer Polytechnic Institute, Polymer Science and Engineering Program, Troy, New York 12180-3590.

## ABSTRACT

Films of PMMA containing azobenzene were prepared by casting from polymer solutions containing the probe or by exposing pre-irradiated films to the vapor of azobenzene. These materials were irradiated at 335 nm and the amount of trans azobenzene which had been photoisomerized was monitored spectrophotometrically. The largest amount of photoisomerization was observed for the pre-irradiated samples which had been penetrated by azobenzene from the vapor, indicating that the created free volume allowed the isomerization to proceed more easily.

## INTRODUCTION

When polymers are exposed to ultraviolet and high energy radiation, changes of chemical properties (scission or crosslinking) can be detected experimentally and should be associated with changes in the physical properties such as the local free volume [1-3] and glass transition temperature [4, 5]. These changes of chemical and physical properties affect the solubility characteristics in the irradiated area of polymer films and play a major role in lithographic materials [1-3].

Degradation of PMMA by various types of radiation such as ultraviolet, x-ray,  $\gamma$ -ray, electron and proton beams has been of interest both from the basic and practical point of view [6, 7]. Exposure of PMMA films to these radiation sources results in reduced molecular weight, the generation of unsaturated bonds by the scission of side chains, the evolution of gaseous products, and the appearance of the characteristic electron spin spectra of propagating [8] and peroxy radicals [9]. These chemical changes should be associated with the increase of local free volume (creation of micropores) in the irradiated PMMA.

A detailed study of the factors affecting the dissolution rate of PMMA film showed that the magnitude of the increase in the dissolution rate of irradiated film could not be entirely attributed to the reduction of the molecular weight [1, 2]. The evolution of gaseous products, i. e., CO, CO<sub>2</sub>, HCO<sub>2</sub>CH<sub>3</sub>, CH<sub>4</sub>, and CH<sub>3</sub>OH, would cause an increase in local free volume in the irradiated film. Ouano observed indirect evidence of micropore formation in the irradiated PMMA from a study of changes in the dissolution rate (S) based on the solvent molecular weight (M<sub>s</sub>) of a homologous series of n-alkyl acetate solvents. As the micropores become more numerous and larger with increasing radiation dose, the diffusion process of butyl acetate and the higher acetate homologs becomes less hindered, thus the break in

the  $\log S$  vs.  $\log M_s$  becomes less pronounced. When PMMA films were prepared containing Meldrum's diazo as a dopant, the dopant acted as a mild retarder of film dissolution [10]. Upon irradiation at 254 nm, CO, N<sub>2</sub> and acetone as photoproducts diffused quickly out of the film leaving microvoids in the PMMA films. This process led to a pronounced acceleration of dissolution in the irradiated areas.

The presence of micropores in the polymer matrix permits increased diffusion compared to the homogenous polymer - penetrant system [11]. Therefore, the formation of micropores should affect the sorption of penetrants in the irradiated PMMA film. There are a variety of methods for measuring the sorption of a penetrant in polymers [11, 12]. However, these methods are not easily employed for the determination of sorption in a microthin film on a silicon wafer substrate. On the other hand, the sorption of a species, which has a very high extinction coefficient ( $\approx 10^4$  l/mol-cm) compared to PMMA film, can penetrate PMMA film and the amount of a reporter molecule such as naphthalene absorbed in the irradiated PMMA films can be easily determined spectrophotometrically.

In recent reviews [13, 14], the dominant factor in the photoisomerization of labels in polymeric solids is the local free volume in the vicinity of the label, because photoisomerization is strongly dependent on the rotational mobility of the label in the matrix. Analyses of the photoisomerization behavior of photochromic labels allows the study of processes such as physical aging, plasticization, and volume dilation caused by glassy deformation to be monitored sensitively. The free volume and the size distribution of free volumes in polymeric systems have been probed by the use of photochromic labels [15, 16]. In this work, azobenzene was used as a molecular label to study the formation of micropores in irradiated PMMA film. Trans azobenzene located in a PMMA matrix is photoisomerized when exposed to UV light of appropriate wavelength. The amount of photoisomerization (trans to cis) of azobenzene irradiated for a specific time was used to probe the formation of micropores in PMMA films by UV irradiation.

## EXPERIMENTAL

### Sorption of Naphthalene and Azobenzene in Irradiated PMMA Films

An irradiated PMMA film on a quartz disk was placed in a chamber containing naphthalene or trans azobenzene crystals, which were used in commercial grade. The sample disks were positioned at about 5 cm from the bottom of the container to avoid contact between the crystals and the films. The closed container was stored in an oven at 50 ~ 60 °C to increase the rate of sublimation of naphthalene or azobenzene. Immediately after the sample was removed from the sorption chamber, its UV absorption spectrum was measured.

## Photoisomerization (Trans to Cis) of Azobenzene in PMMA Films

PMMA films containing trans azobenzene were exposed to a flash UV light from a PRA flash lamp (Model 6199A) by using a narrow band interference filter ( $335 \pm 10$  nm). The UV spectra of samples changed photochemically were measured with a Perkin Elmer UV spectrophotometer immediately after a given number of flashes.

## RESULTS AND DISCUSSINS

There are a variety of methods for measuring the sorption of a penetrant in polymer films. The most general procedures involve gravimetric and volumetric determinations. However, these methods are not easily employed for the determination of sorption in an ultra-thin film on a silicon wafer. On the other hand, sorption in PMMA films can be measured spectrophotometrically by using aromatic compounds as a probe. Naphthalene (solubility parameter,  $\delta = 9.9$  [cal/cm<sup>3</sup>]<sup>1/2</sup>) was chosen as the sorption species because its vapor does not dissolve PMMA films at 60 °C and it is sublimed at a rate slow enough to be disregarded with respect to the loss of naphthalene during the spectroscopic measurement.

UV-irradiated and unexposed PMMA films were exposed to naphthalene vapor sublimed at 60 °C in the same vessel. The difference spectra of UV-irradiated PMMA films before and after naphthalene sorption are shown in Figure 1.

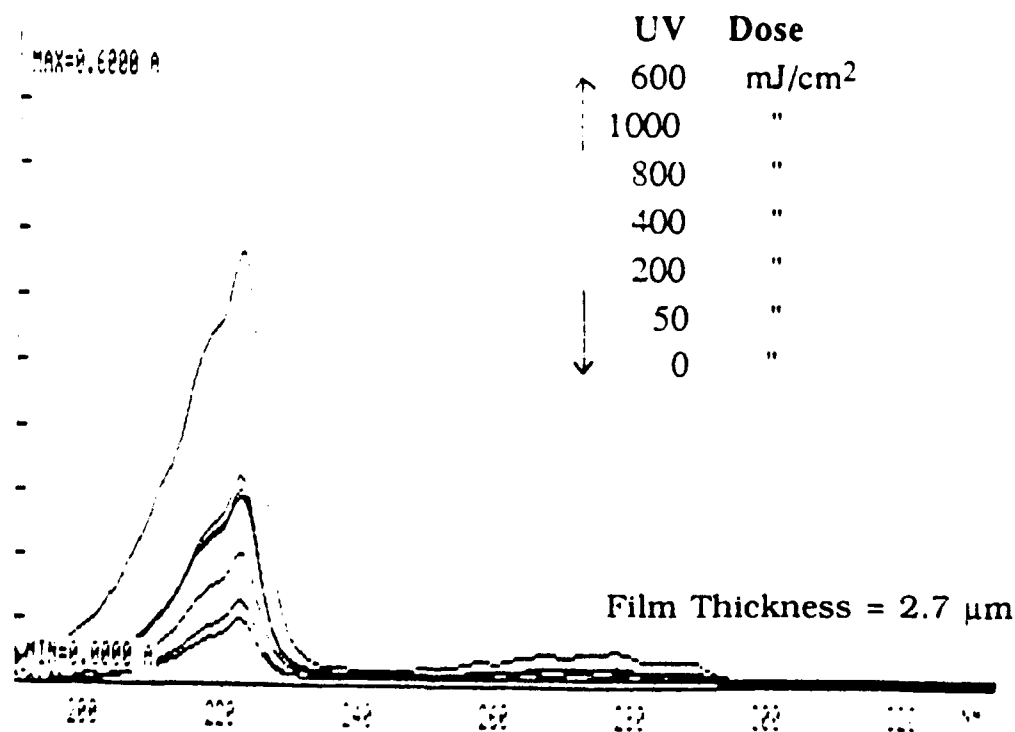


Figure 1. UV Difference Spectra of UV-Irradiated PMMA Films before and after Naphthalene Sorption at 60 °C for 3 Hours.

The amount of naphthalene imbibed by these samples was dependent on the incident dose. Under the same conditions, irradiated films imbibed more azobenzene than unirradiated films or irradiated films which had been annealed above  $T_g$ . PMMA films irradiated with electron and proton beams showed a similar trend of naphthalene sorption. The concentration of absorbed material was calculated from the UV difference spectra by using Beer's equation and is plotted in Figure 2. The absorption of naphthalene in PMMA films increases with longer exposure to radiation, then decreases beyond a certain dose. The azobenzene sorption in UV-irradiated PMMA films showed the same trend as naphthalene. These data indicate that the creation of micropores in PMMA film by radiation could be indirectly determined by the sorption. Further, the creation of the micropores may have been limited by recombination of polymeric fragments beyond a certain dose.

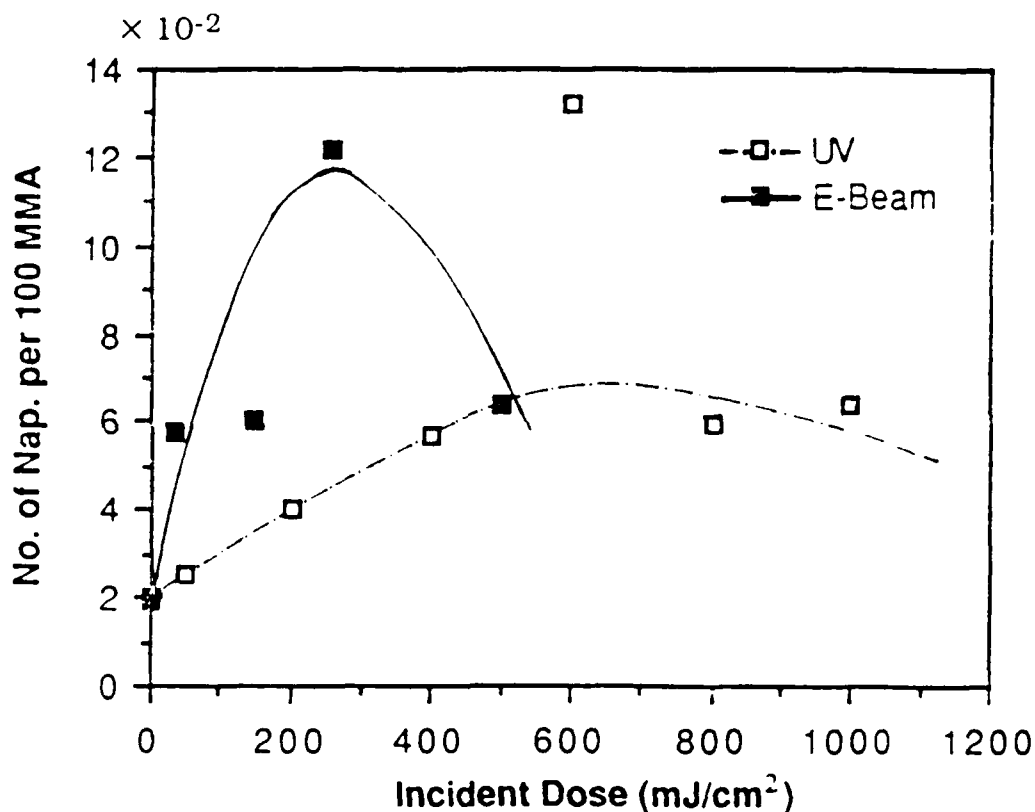


Figure 2. Plot of Naphthalene Sorption vs. Incident Dose in PMMA Film ( $\approx 3 \mu\text{m}$ ) at  $60^\circ\text{C}$  for 3 Hours.

It was reported that the free volume in the polymer matrix could be probed by the use of photochromic labels [13-16]. Analysis of the photoisomerization behavior of photochromic labels within local free volume should be applicable to the study of the creation of micropores in a PMMA film irradiated with UV light. In this work, azobenzene was used to monitor the creation of micropores spectrophotometrically. Azobenzene exists as the extended trans isomer under normal conditions, but upon irradiation at 335 nm it is isomerized to the compact cis isomer by rotation about the weakened  $\text{N}=\text{N}$  bond in the excited state. Clearly this isomerization process will be affected by the amount of space (local free volume or microporosity) available on the molecular level as long as it is small compared to the

molecular dimensions of the probe. The amounts of photoisomerization (trans to cis) were compared in the various samples prepared by different methods. Figure 3 shows changes in the UV spectra of azobenzene in PMMA film upon exposure to UV light at 335 nm.

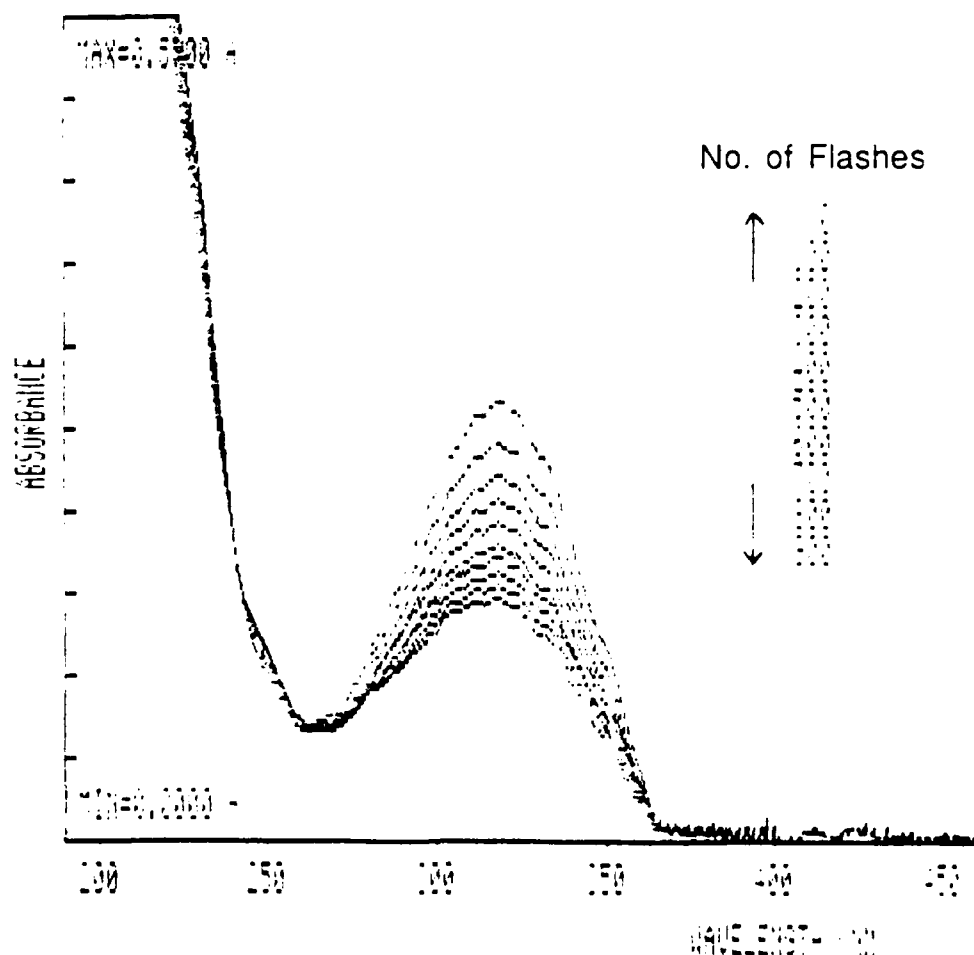


Figure 3. Changes of the UV Spectrum of Azobenzene in Irradiated PMMA Film by Exposure to UV Light ( $335 \pm 10$  nm).

The amount of photoisomerization of azobenzene can be determined from the changes in the UV spectrum, assuming that the thermal and photochemical re-isomerization (cis to trans) is negligible in the early stages. Four PMMA samples, where azobenzene would be located in different amounts of free volume, were prepared as described below.

- (A) Irradiated PMMA film was exposed to azobenzene vapor at 55 °C for 24 hours. Most of the azobenzene would enter micropores created by degradation of PMMA by UV light.
- (B) A benzene solution of PMMA containing azobenzene was used for spin-coating. When the resulting thin film was baked at 130 °C for 30 minutes, only azobenzene remained in the PMMA film.
- (C) Azobenzene was sorbed in PMMA film by exposing unirradiated films to azobenzene vapor at 120 °C.
- (D) Irradiated PMMA film was exposed to azobenzene vapor at 55 °C and annealed at 120 °C in the presence of excess

azobenzene to prevent its loss during the annealing process. The micropores should be collapsed and azobenzene would be contained in the original (before irradiation) free volume of PMMA film.

The concentration of azobenzene in PMMA was in the range of 0.3 ~ 1.3 molecules per 100 MMA repeating units. The extent of photoisomerization of azobenzene in Table I clearly shows the dependence on the method of sample preparation.

Table I. Photoisomerization of Azobenzene from Trans to Cis by  $335 \pm 10$  nm UV Light.

| Samples |  | Photoisomerization<br>(trans to cis) |             | Concentration<br>of azobenzene<br>per 100 repeating units |
|---------|--|--------------------------------------|-------------|---|
|         |  | 100 flashes                          | 200 flashes |   |
| A       | AZB diffused<br>into irradiated PMMA film            | 12.9 %                               | 30.0 %      | 0.5 AZB/100 MMA   |
|         |  | 13.8 %                               | 25.0 %      | 0.3 AZB/ "  |
| B       | AZB co-cast in PMMA film                             | 7.4 %                                | 10.8 %      | 0.6 AZB/ "  |
|         |  | 8.4 %                                | 15.3 %      | 1.3 AZB/ "  |
| C       | AZB diffused into PMMA film                          | 7.5 %                                | 13.7 %      | 1.1 AZB/ "  |
|         |  | 7.5 %                                | 15.2 %      | 0.5 AZB/ "  |
| D       | AZB diffused and annealed<br>in irradiated PMMA film | 9.9 %                                | 13.2 %      | 0.6 AZB/ "  |
|         |  | 9.3 %                                | 18.2 %      | 0.5 AZB/ "  |

The largest amount of photoisomerization was observed for the pre-irradiated samples (A) which has been penetrated by azobenzene from the vapor, indicating the created free volume allowed the isomerization to proceed more easily. This result is direct evidence that a larger local free volume was created in PMMA films after UV-irradiation.

#### ACKNOWLEDGEMENTS

We thank Mr. Y.-S. Kim and Prof. C. S. P. Sung at the University of Connecticut for their willingness to assist and advise us on the photoisomerization experiments with their flash lamp.

#### REFERENCES

1. A. C. Ouano, Polym. Engr. Sci. 18 (4), 306 (1978).
2. A. C. Ouano, in Materials for Microlithography: Radiation



Sensitive Polymers, edited by L. F. Thompson, C. G. Willson and M. J. Frechet (ACS Symposium Series 266, Washington, D. C., 1984), pp. 79 ~ 90.

3. W. M. Moreau, Optical Engr. 22 (2), 181 (1983).
4. J. W. Martin, J. Appl. Poly. 29, 777 (1984).
5. A. R. Schultz, P. Frank, B. F. Griffing, and A. L. Young, J. Polym. Sci., Polym. Phys. 23, 1749 (1985).
6. J. -O. Choi, J. A. Moore, J. C. Corelli, J. P. Silverman, and H. Bakhru, J. Vac. Sci. Technol. B (6), 2286 (1988).
7. J. A. Moore, and J. -O. Choi, Polym. Preprints 30, 335 (1989).
8. H. Hiraoka, IBM J. Res. Dev., 21, 121 (1977).
9. R. M. Tarro, J. T. Warden, J. C. Corelli, J. A. Moore, A. J. Steckl, and, S. Kumar, Microcircuit Engineering 84, edited by A. Heuberger and H. Beneking (Academic Press, London), 1985, p. 537.
10. W. Limm, and M. A. Winnik, Proceedings of Photopolymers: Processes and Materials (Society of Plastics Engineers, Inc., Mid-Hudson Section, 1988), pp. 215~233.
11. D. Machin and C. E. Rogers, Encyclopedia of Polymer Science and Technology, Vol. 12 (Interscience Publishers, New York, 1964), pp. 679~685.
12. S. Matsuoka, and T. K. Kwei, in Macromolecules: An Introduction to Polymer Science, edited by F. A. Bovey and F. H. Winslow (Academic Press, New York, 1979), pp. 398~406.
13. J. L. R. Williams, and R. C. Daly, Prog. Polym. Sci. 5, 61 (1977).
14. K. Horie, and I. Mita, Advances in Polymer Science 88, Specialty Polymers/ Polymer Physics. (Springer-Verlag, Berlin, 1989), pp. 106~128.
15. L. Lamarre, and C. S. P. Sung, Macromolecules 16, 1729 (1983).
16. W.-C. Yu, and C. S. P. Sung, Macromolecules 21, 365 (1988).

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (2)  
Chemistry Division, Code 1113  
800 North Quincy Street  
Arlington, Virginia 22217-5000

Commanding Officer (1)  
Naval Weapons Support Center  
Dr. Bernard E. Douda  
Crane, Indiana 47522-5050

Dr. Richard W. Drisko (1)  
Naval Civil Engineering  
Laboratory  
Code L52  
Port Hueneme, CA 93043

David Taylor Research Center (1)  
Dr. Eugene C. Fischer  
Annapolis, MD 21402-5067

Dr. James S. Murday (1)  
Chemistry Division, Code 6100  
Naval Research Laboratory  
Washington, D.C. 20375-5000

Dr. Robert Green, Director (1)  
Chemistry Division, Code 385  
Naval Weapons Center  
China Lake, CA 93555-6001

Chief of Naval Research (1)  
Special Assistant for Marine  
Corps Matters  
Code 00MC  
800 North Quincy Street  
Arlington, VA 22217-5000

Dr. Bernadette Eichinger (1)  
Naval Ship Systems Engineering  
Station  
Code 053  
Philadelphia Naval Base  
Philadelphia, PA 19112

Dr. Sachio Yamamoto (1)  
Naval Ocean Systems Center  
Code 52  
San Diego, CA 92152-5000

Dr. Harold H. Singerman (1)  
David Taylor Research Center  
Code 283  
Annapolis, MD 21402-5067

Defense Technical Information Center(2)  
Building 5, Cameron Station  
Alexandria, VA 22314